



Non-destructive testing of welds — Magnetic particle testing of welds

The European Standard EN 1290:1998, with the incorporation of amendment A1:2002, has the status of a British Standard

ICS 25.160.40

National foreword

This British Standard is the English language version of EN 1290:1998, including amendment A1:2002.

The start and finish of text introduced or altered by amendment is indicated in the text by tags $\boxed{A1}$ $\langle A1 \rangle$. Tags indicating changes to CEN text carry the number of the CEN amendment. For example, text altered by CEN amendment A1 is indicated by $\boxed{A1}$ $\langle A1 \rangle$.

As agreed by CEN/TC 121/SC 5 resolution 134/2000 and in accordance with amendment A1:2002, the term “examination” has been replaced by “testing” throughout the document.

The UK participation in its preparation was entrusted to Technical Committee WEE/46, Non-destructive examination, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 15 and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

This British Standard, having been prepared under the direction of the Engineering Sector Board, was published under the authority of the Standards Board and comes into effect on 15 June 1998

© BSI 30 October 2002

Amendments issued since publication

| Amd. No. | Date | Comments |
|----------|-----------------|-----------------------|
| 13987 | 30 October 2002 | See national foreword |
| | | |
| | | |
| | | |

ISBN 0 580 29630 X

ICS 25.160.40

Descriptors: Welded joints, ferromagnetic materials, quality control, non-destructive tests, detection, weld defects, magnetic particle testing, surface treatment

English version

Non-destructive examination of welds — Magnetic particle examination of welds (includes amendment A1:2002)

Contrôle non destructif des assemblages soudés —
Contrôle par magnétoscopie des assemblages soudés
(inclut l'amendement A1:2002)

Zerstörungsfreie Prüfung von
Schweißverbindungen —
Magnetpulverprüfung von Schweißverbindungen
(enthält Änderung A1:2002)

This European Standard was approved by CEN on 26 January 1998. Amendment A1 was approved by CEN on 28 April 2002.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart 36, B-1050 Brussels

Foreword

This European Standard has been prepared by Technical Committee CEN/TC 121, Welding, the secretariat of which is held by DS.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 1998, and conflicting national standards shall be withdrawn at the latest by August 1998.

This European Standard has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports essential requirements of EU Directive(s).

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Foreword to amendment A1

This document EN 1290:1998/A1:2002 has been prepared by Technical Committee CEN/TC 121, Welding, the secretariat of which is held by DS.

This amendment to the European Standard EN 1290:1998 shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by November 2002, and conflicting national standards shall be withdrawn at the latest by November 2002.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports essential requirements of EU Directive(s).

For relationship with EU Directive(s), see informative Annex ZA, which is an integral part of this document.

Annex A is informative.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Malta, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Contents

| | Page |
|---|------|
| Foreword | 2 |
| 1 Scope | 3 |
| 2 Normative references | 3 |
| 3 Definitions | 3 |
| 4 Safety precautions | 3 |
| 5 General | 3 |
| 5.1 Information | 3 |
| 5.2 Personnel qualification | 4 |
| 5.3 Surface conditions and preparation | 4 |
| 5.4 Magnetizing | 4 |
| 5.5 Application techniques | 5 |
| 5.6 Detecting media | 12 |
| 5.7 Viewing conditions | 12 |
| 5.8 Application of detecting media | 12 |
| 5.9 Overall performance test | 12 |
| 5.10 False indications | 12 |
| 5.11 Recording of indications | 12 |
| 5.12 Demagnetization | 13 |
| 5.13 Test report | 13 |
| Annex A (informative) Sensitivity aspects | 14 |
| Annex ZA (informative) Clauses of this European Standard addressing essential requirements or other provisions of EU directives | 15 |

1 Scope

This standard specifies magnetic particle testing techniques for the detection of surface imperfections in ferromagnetic welds, including the heat-affected zones, using the magnetic method. Techniques recommended are suitable for most welding processes and joint configurations. Variations to the basic techniques that will provide a higher or lower testing sensitivity are described in Annex A.

Techniques for testing of welds, with geometries in accordance with those shown in Table 1, Table 2 and Table 3, can be used directly from this standard.

Acceptance levels for indications are described in EN 1291.

2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN 473, *Qualification and certification of NDT personnel — General principles.*

EN 1291, *Non-destructive testing of welds — Magnetic particle testing of welds — Acceptance levels.*

EN 12062, *Non-destructive testing of welds — General rules for metallic materials.*

Ⓐ) EN ISO 3059, *Non-destructive testing — Penetrant testing and magnetic particle testing — Viewing conditions.* (ISO 3509:2001) Ⓐ)

3 Definitions

For the purposes of this standard, the definitions given in EN 12062 apply.

4 Safety precautions

European, national and local safety and environment protection regulations shall be observed at all times. Special consideration shall be given to toxic flammable and/or volatile materials, electrical safety and unfiltered UV radiation.

5 General

5.1 Information

5.1.1 Ⓐ) *Items to be specified*

Before carrying out magnetic particle testing, the following items, if applicable, shall be specified: Ⓐ)

- a) specific testing procedure;
- b) certification requirements for NDT personnel;
- c) extent of coverage;
- d) state of manufacture;
- e) testing techniques to be used;
- f) overall performance test;
- g) demagnetization;
- h) acceptance level;
- i) action necessary for unacceptable indications.

5.1.2 *Additional information*

Prior to testing, the following additional information can be required:

- a) type and testing of the parent and weld materials;
- b) welding process;
- c) location and extent of welds to be tested;
- d) joint preparation and dimensions;
- e) location and extent of any repairs;
- f) post-weld treatment (if any);
- g) surface conditions.

Operators can ask for further information that could be helpful in determining the nature of any indications detected.

5.2 **Personnel qualification**

Personnel performing non-destructive testing in accordance with this standard shall be qualified to an appropriate level in accordance with EN 473 or an equivalent standard at an appropriate level in the relevant industrial sector.

5.3 **Surface conditions and preparation**

Areas to be tested shall be free from scale, oil, grease, weld spatter, machining marks, dirt, heavy and loose paint, and any other foreign matter that can affect sensitivity.

It can be necessary to improve the surface condition, e.g. by abrasive paper or local grinding, to permit accurate interpretation of indications.

Cleaning and preparation of surfaces shall not be detrimental to the material, the surface finish or the magnetic testing media.

5.4 **Magnetizing**

5.4.1 *Magnetizing equipment*

Unless otherwise agreed, the following types of alternating-current magnetizing equipment shall be used:

- a) electromagnetic yokes;
- b) current flow equipment with prods;
- c) adjacent or threading conductors, or coil techniques.

Direct-current magnetization or permanent magnets A_1 may be used if specified A_1 .

The magnetizing equipment used shall comply with the requirements of relevant European Standards. Prior to the publication of European Standards related to the subject, the corresponding national standards may be used.

Where prods are used, precautions shall be taken to minimize overheating, burning or arcing at the contact tips. Removal of arc burns shall be carried out where necessary. The affected area shall be tested by a suitable method to ensure the integrity of the surface.

5.4.2 Verification of magnetization

For most weldable ferromagnetic materials, a tangential magnetic field strength of 2 kA/m to 6 kA/m (r.m.s.) is recommended.

Verification of the magnetic field strength shall be carried out using one of the following methods:

- a) a component containing fine natural or artificial imperfections in the least favourable locations;
- b) measurement of the tangential field strength as close as possible to the surface using a Hall effect probe. The appropriate tangential field strength can be difficult to measure close to abrupt changes in the shape of a component, or where flux leaves the surface of a component;
- c) $\overline{A_1}$ calculation of the approximate current value in order to achieve the recommended tangential field strength. The calculations can be based on the current values specified in Table 2 and Table 3; $\overline{A_1}$
- d) other methods based on established principles.

NOTE Flux indicators, placed in contact with the surface under test, can provide a guide to the magnitude and direction of the tangential field, but should not be used to verify that the field strength is acceptable.

5.5 Application techniques

5.5.1 Field directions and examination area

The detectability of an imperfection depends on the angle of its major axis with respect to the direction of the magnetic field. This is explained for one direction of magnetization in Figure 1.

To ensure detection of imperfections in all orientations, the welds shall be magnetized in two directions approximately perpendicular to each other with a maximum deviation of 30°. This can be achieved using one or more magnetization methods.


$\overline{A_1}$ Testing in only one field direction may be carried out if specified. $\overline{A_1}$

When testing involves the use of yokes or prods, there will be an area of the component, in the vicinity of each pole piece or tip, that will be impossible to test due to excessive magnetic field strength, usually shown by furring of particles.

Care shall be taken to ensure adequate overlap of the testing areas as shown in Figure 2 and Figure 3.

5.5.2 Typical magnetic testing techniques


Applications of magnetic particle testing techniques to common weld joint configurations are shown in Table 1, Table 2 and Table 3. Values are given for guidance purposes only. Where possible, the same directions of magnetization, and field overlaps, should be used for other weld geometries to be tested. The dimension, d , the flux current path in the material, shall be greater than or equal to the width of the weld and the heat-affected zone +50 mm, and in all cases the weld and the heat-affected zone shall be included in the effective area. The approximate $\overline{A_1}$ direction $\overline{A_1}$ of magnetization related to the weld direction shall be specified.

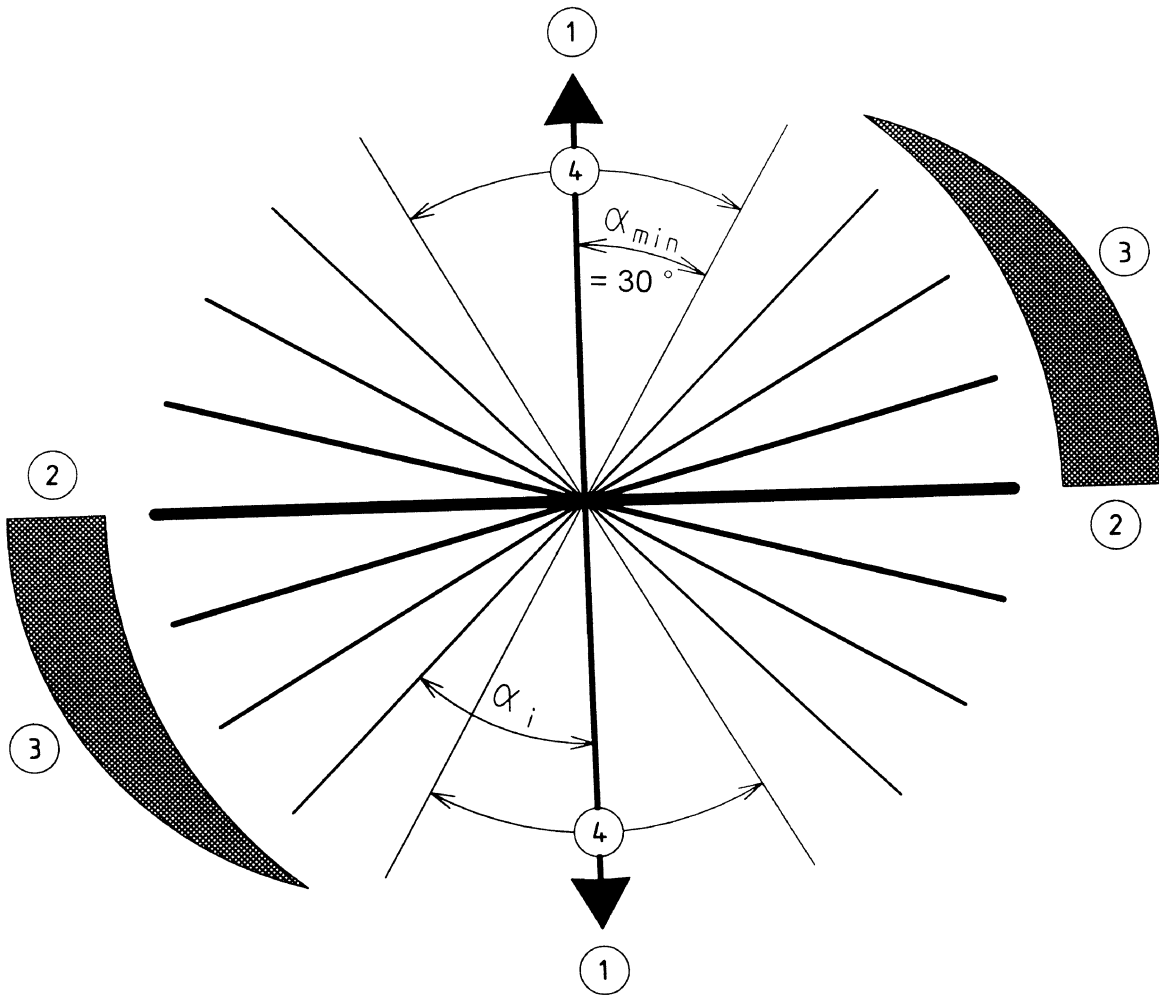

- 1 Magnetic field direction
- 2 Optimum sensitivity
- 3 Reducing sensitivity
- 4 Insufficient sensitivity

α is the angle between the magnetic field and the direction of the imperfection
 α_{min} is the minimum angle for imperfection detection
 α_i is an example of imperfection orientation

Figure 1 — Directions of detectable imperfections

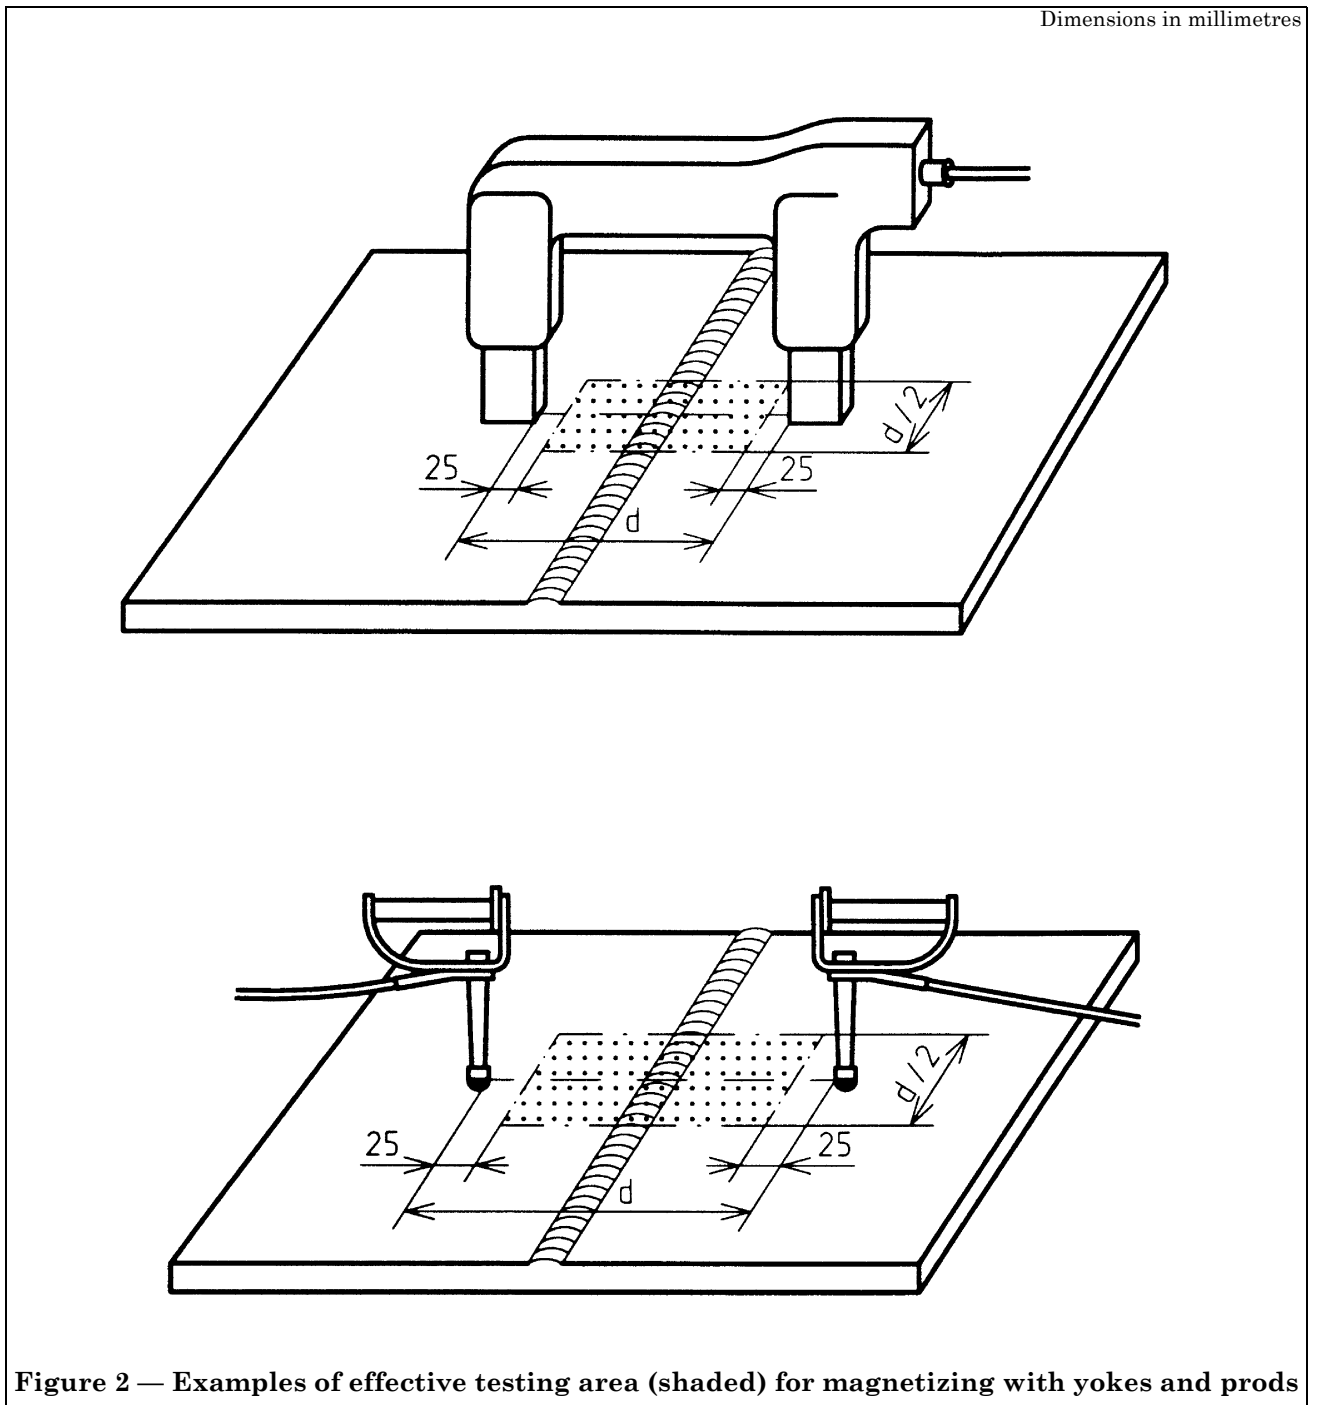

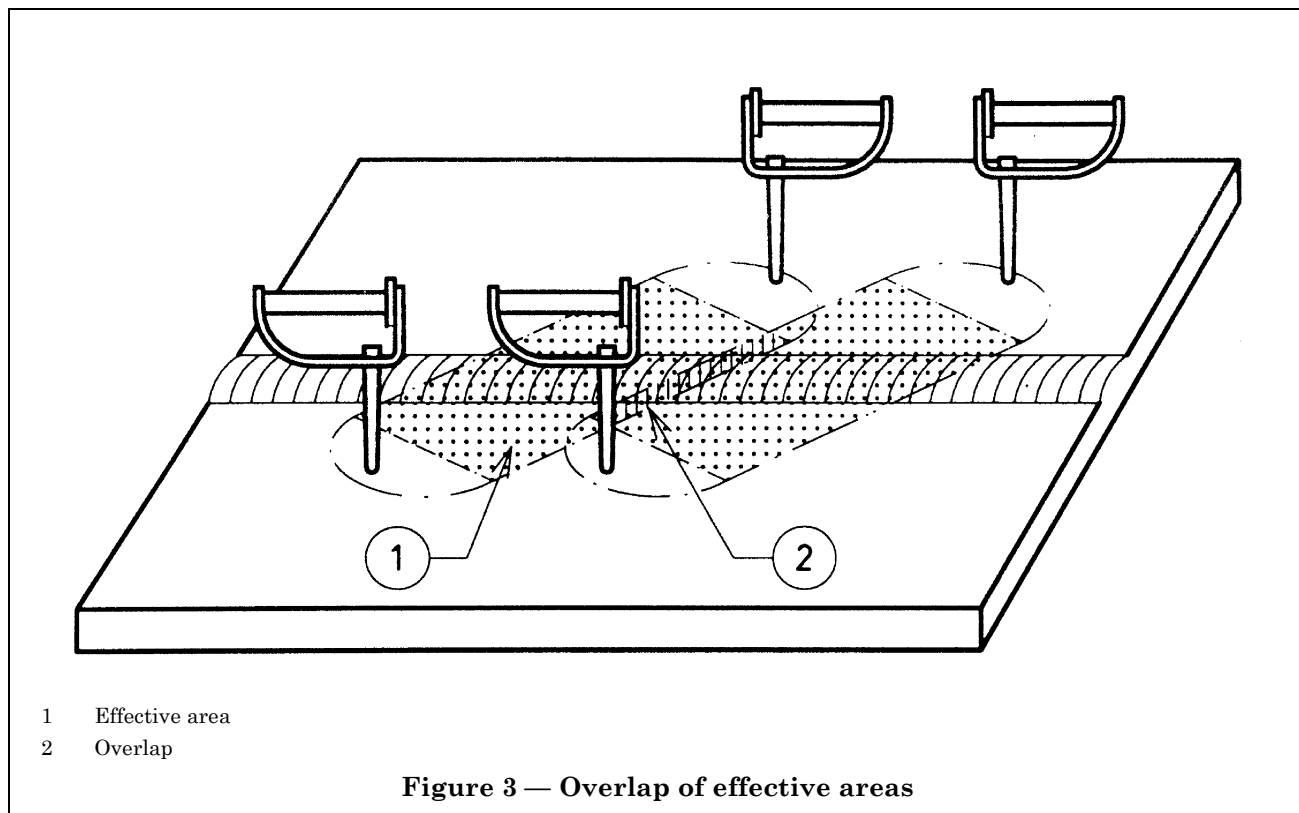


Table 1 — Typical magnetizing techniques for yokes

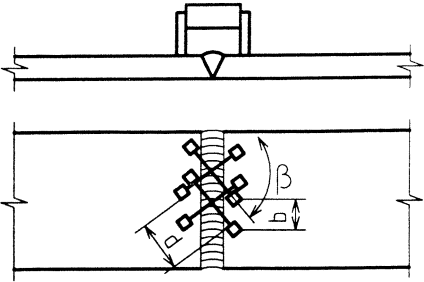
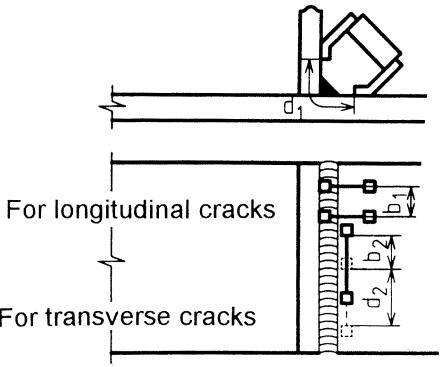
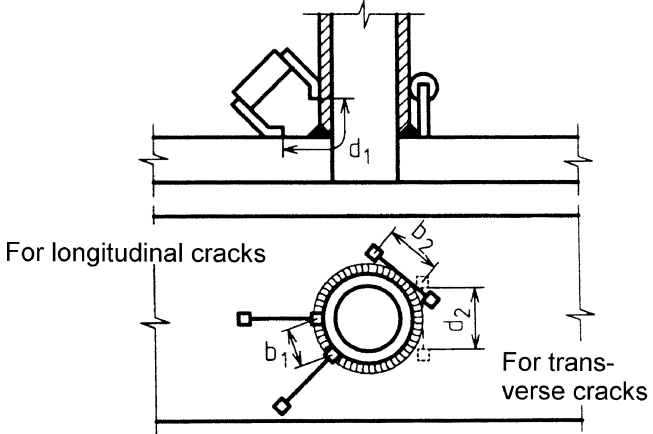
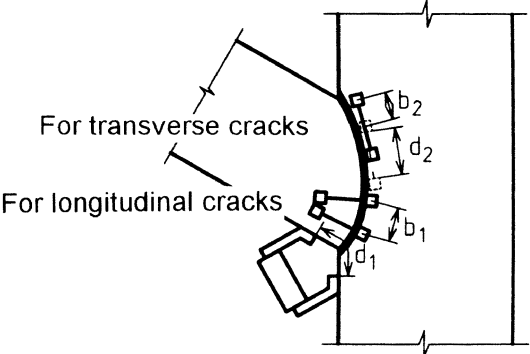
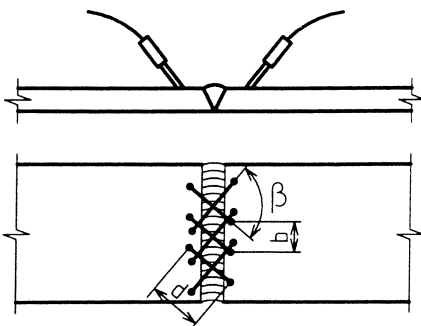
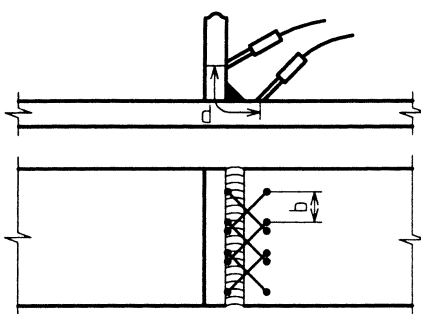
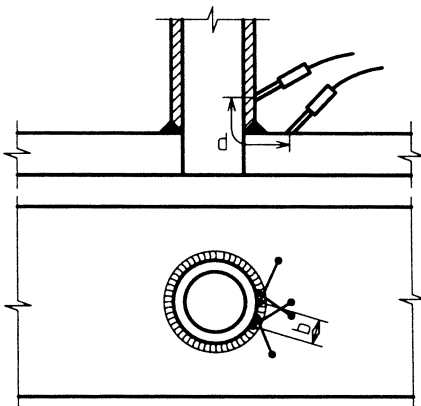
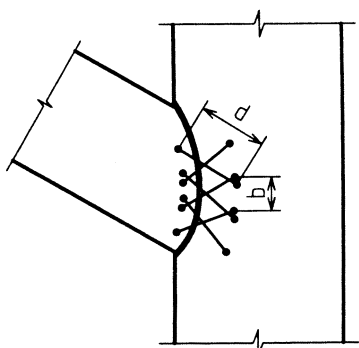
| | | Dimensions in millimetres |
|--|--|---|
|  | | $d \geq 75$ $b \leq d/2$ $\beta \approx 90^\circ$ |
|  <p>For longitudinal cracks</p> <p>For transverse cracks</p> | | $d_1 \geq 75$ $b_1 \leq d_1/2$ $b_2 \leq d_2 - 50$ $d_2 \geq 75$ |
|  <p>For longitudinal cracks</p> <p>For transverse cracks</p> | | $d_1 \geq 75$ $d_2 > 75$ $b_1 \leq d_1/2$ $b_2 \leq d_2 - 50$ |
|  <p>For transverse cracks</p> <p>For longitudinal cracks</p> | | $d_1 \geq 75$ $d_2 \geq 75$ $b_1 \leq d_1/2$ $b_2 \leq d_2 - 50$ |




Table 2 — Typical magnetizing techniques for prods, using a magnetizing current $\geq 5 \text{ A/mm (r.m.s.) prod spacing}$

Dimensions in millimetres

| | |
|---|---|
|  | $d \geq 75$ $b \leq d/2$ $\beta \approx 90^\circ$ |
|  | $d \geq 75$ $b \leq d/2$ |
|  | $d \geq 75$ $b \leq d/2$ |
|  | $d \geq 75$ $b \leq d/2$ |

Licensed Copy: Tom Magee, Howden Power, 15 May 2003, Uncontrolled Copy, (c) BSI

Table 3 — Typical magnetizing techniques for flexible cables or coils
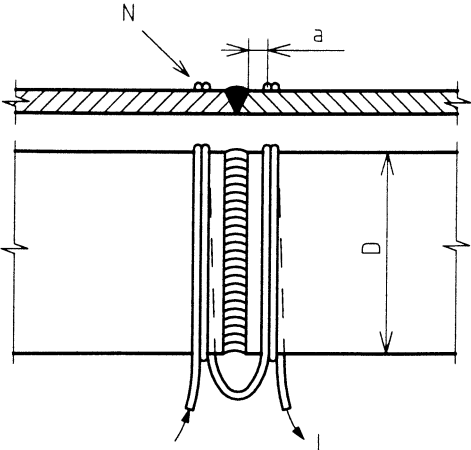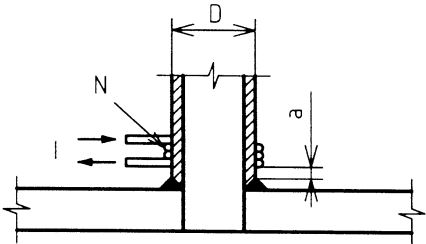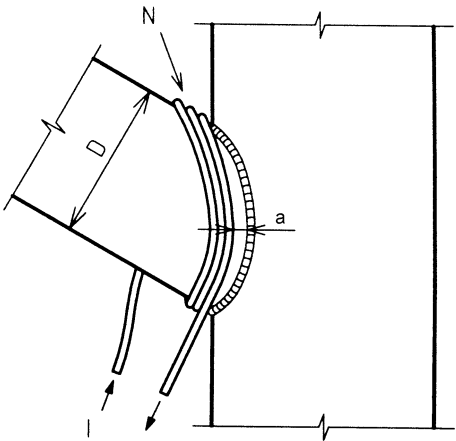
| | | Dimensions in millimetres |
|--|--|-------------------------------------|
|  <p>For longitudinal cracks</p> | | $20 \leq a \leq 50$ $NI \geq 8D$ |
|  <p>For longitudinal cracks</p> | | $20 \leq a \leq 50$ $NI \geq 8D$ |
|  <p>For longitudinal cracks</p> | | $20 \leq a \leq 50$ $NI \geq 8D$ |
| <p><i>N</i> is the number of turns; <i>I</i> is the current (r.m.s.); <i>a</i> is the distance between weld and coil or cable.</p> | | |

5.6 Detecting media

5.6.1 General

Detection media may be either in dry powder or liquid form and shall comply with the requirements of relevant European Standards. Prior to the publication of European Standards related to the subject, the corresponding national standards may be used.

5.6.2 Verification of detecting media performance

Verification of the detecting media shall be carried out periodically to confirm continuing satisfactory performance.

The verification shall be carried out on components having known or artificial surface imperfections, or on pre-magnetized reference pieces.

Indications obtained with the medium to be verified shall be compared against those obtained from a medium having a known and acceptable performance. For this purpose the reference indications may be:

- a) real imperfections;
- b) photograph(s); or
- c) replica(s).

5.7 Viewing conditions

The viewing conditions shall meet the requirements of \square_{A1} EN ISO 3059 \square_{A1} .

5.8 Application of detecting media

After the object has been prepared for \square_{A1} testing, the \square_{A1} detecting medium shall be applied by spraying, flooding or dusting immediately prior to and during the magnetization. Following this, time shall be allowed for indications to form before removal of the magnetic field.

When magnetic suspensions are used, the magnetic field shall be maintained within the object until the majority of the suspension carrier liquid has drained away from the testing surface. This will prevent any indications being washed away.

Depending on the material being tested, its surface condition and magnetic permeability, indications will normally remain on the surface even after removal of the magnetic field, due to residual magnetism within the part. However, the presence of residual magnetism shall not be presumed; post-evaluation techniques after removal of the prime magnetic field source can be permitted only when a component has been proven by an overall performance test to retain magnetic indications.

5.9 Overall performance test

Where \square_{A1} defined by specification \square_{A1} , an overall performance test of the system sensitivity, for each specific procedure shall be carried out on site. The test shall be designed to ensure a proper functioning of the entire chain of parameters including the equipment, the magnetic field strength and direction, surface characteristics, detecting media and illumination.

The most reliable test is to use representative test pieces containing real imperfections of known type, location, size and size distribution. Where these are not available, fabricated test pieces with artificial imperfections, or flux shunting indicators of the cross type or shim type may be used. The test pieces shall be demagnetized and free from indications resulting from previous tests.

5.10 False indications

False indications which may mask relevant indications can arise for many reasons, e.g. undercut and changes in magnetic permeability, i.e. the heat-affected zone. Where masking is suspected, the examination surface shall be dressed, or suitable alternative testing methods can be used.

5.11 Recording of indications

Indications can be recorded in one or more of the following ways by using:

- a) description in writing;
- b) sketches;
- c) photography;

- d) transparent adhesive tape;
- e) transparent varnish for “freezing” the indication on the surface tested;
- f) A_1 peelable A_1 contrast aids;
- g) video recording;
- h) epoxy or chemical magnetic particle mixtures;
- i) magnetic tapes;
- j) electronic scanning.

5.12 Demagnetization

After testing of welds with alternating current, residual magnetization will normally be low and there will generally be no need for demagnetization of the object under test.

A_1 If the demagnetization is required by specification, it shall be carried out using a specified method and to a defined level.¹⁾ A_1

5.13 Test report

A test report shall be prepared.

A_1 The following information should be included in the test report unless otherwise specified: A_1

- a) name of the company carrying out the test;
- b) the object tested;
- c) date of testing;
- d) parent and weld materials;
- e) post-weld heat treatment;
- f) type of joint;
- g) material thickness;
- h) welding process;
- i) temperature of the test object, if outside normal ambient temperature;
- j) identification of testing procedure and description of the parameters used, including:
 - type of magnetization;
 - type of current;
 - detection media;
 - viewing conditions.
- k) details and results of the overall performance test, where applicable;
- l) acceptance levels;
- m) description and location of all recordable indications;
- n) test results with reference to acceptance level;
- o) names, relevant qualification and signatures of personnel who carried out the testing.

¹⁾ For metal-cutting processes, a typical residual field strength value of $H \leq 0,4$ kA/m is recommended.

Annex A (informative)

Sensitivity aspects

A.1 Surface conditions and preparation

The maximum testing sensitivity that can be achieved by any magnetic testing method is dependent on many variables but can be seriously affected by the surface roughness of the object and any irregularities present. In some cases it can be necessary to:

- dress undercut and surface irregularities by grinding;
- remove or reduce the weld reinforcement.

Surfaces covered with a thin non-magnetic paint, e.g. a primer may also be tested, provided that the paint surface is unbroken and the thickness of the coating does not exceed 50 µm. Above this thickness, the sensitivity of the method decreases and can be specifically determined before proceeding with the testing.

A.2 Magnetizing equipment characteristics

The use of alternating current gives the best sensitivity for detecting surface imperfections.

Yokes produce an adequate magnetic field in simple butt-welds, but where the flux is reduced by gaps or the path is excessive through the object, as in T-joints, a reduction of sensitivity can occur.

For complex joint configurations, e.g. A_1 branch connections A_1 with an inclined angle of less than 90°, testing using yokes might be inadequate. In these cases, prods or cable wrapping with current flow will prove more suitable.

A.3 Magnetic field strength and permeability

The field strength required to produce an indication strong enough to be detected during magnetic particle testing is dependent mainly on the magnetic permeability of the object.

Generally, magnetic permeability is high in softer magnetic materials, e.g. low-alloy steels, and low in harder magnetic materials, e.g. martensitic steels. Because permeability is a function of the magnetizing current, low-permeability materials usually require application of a higher magnetization value than softer alloys, to produce the same flux density. It is essential, therefore, to establish that flux density values are adequate before beginning the magnetic particle testing.

A.4 Detecting media

Magnetic particle suspensions will usually give a higher sensitivity for detecting surface imperfections than dry powders.

Fluorescent magnetic detection media usually give a higher test sensitivity than colour-contrast media, because of the higher contrast between the darkened background and the fluorescent indication. The sensitivity of the fluorescent method will, nevertheless, decrease in proportion to any increase in the roughness of the surface to which magnetic particles adhere, and can cause a disturbing background fluorescence.

Where the background illumination cannot be adequately lowered, or where background fluorescence is disturbing, coloured detection media in conjunction with the smoothing effect of a contrast aid will usually give a better sensitivity.

Annex ZA (informative)**Clauses of this European Standard addressing essential requirements or other provisions of EU directives**

This European Standard has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association and supports essential requirements of EU 97/23/EC of the European Parliament and the Council of 29 May 1997 on the approximation of the laws of the Member States concerning pressure equipment.

WARNING Other requirements and other EU Directives may be applicable to the product(s) falling within the scope of this standard.

The following clauses of this standard as detailed in Table ZA.1 and Table ZA.2, are likely to support requirements of the Directives 97/23/EC, and 87/404/EEC.

Compliance with these clauses of this standard provides one with means of conforming to the specific essential requirements of the Directives concerned and associated EFTA regulations.

Table ZA.1 — Correspondence between this European Standard and Directive 97/23/EC

| Clauses/sub-clauses of this European Standard | Essential requirements of Directive 97/23/EC | Qualifying remarks/notes |
|---|--|--------------------------|
| All | Annex I, § 3.2 | Non-destructive tests |

Table ZA.2 — Correspondence between this European Standard and Directive 87/404/EC

| Clauses/sub-clauses of this European Standard | Essential requirements of Directive 87/404/EEC | Qualifying remarks/notes |
|---|--|----------------------------|
| All | Annex I, § 3.2 | Welds on pressurized parts |

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001. Fax: +44 (0)20 8996 7001. Email: orders@bsi-global.com. Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: info@bsi-global.com.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001. Email: membership@bsi-global.com.

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager. Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553. Email: copyright@bsi-global.com.